

# Electrosynthesis of $\text{ReS}_4$ . XAS Analysis of $\text{ReS}_2$ , $\text{Re}_2\text{S}_7$ , and $\text{ReS}_4$

Daniel E. Schwarz,<sup>†</sup> Anatoly I. Frenkel,<sup>\*,‡</sup> Ralph G. Nuzzo,<sup>\*,†</sup>  
Thomas B. Rauchfuss,<sup>\*,†</sup> and Appathurai Vairavamurthy<sup>§</sup>

Department of Chemistry and the Frederick Seitz Materials Research Laboratory,  
University of Illinois at Urbana-Champaign, Urbana, Illinois 61801, Department of Physics,  
Yeshiva University, 245 Lexington Avenue, New York, New York 10016, and Department of  
Energy Sciences and Technology, Brookhaven National Laboratory, Upton, New York 11973

Received June 11, 2003. Revised Manuscript Received October 14, 2003

Solutions of  $\text{ReS}_4^-$  undergo electro-oxidation at 0.5 V vs  $\text{Ag}|\text{AgCl}$  to give black, amorphous  $\text{ReS}_4$  via a process that can be reversed at  $-0.9$  V. The oxidative polymerization can also be effected chemically using either  $\text{I}_2$  or ferrocenium as oxidants. X-ray absorption spectroscopy (XAS) suggests that the phases  $\text{Re}_2\text{S}_7$  and  $\text{ReS}_4$  are closely related structurally. The XAS data were calibrated with studies on  $[\text{ReS}_4]^-$  and crystalline  $\text{ReS}_2$ . For both  $\text{ReS}_4$  and  $\text{Re}_2\text{S}_7$  XAS data show the presence of both  $\text{S}^{2-}$  and  $\text{S}_2^{2-}$ , with  $\text{S}^{2-}$  being less abundant than  $\text{S}_2^{2-}$ . The presence of terminal sulfides ( $r_{\text{Re}=\text{S}} \sim 2.14$  Å) was ruled out by the EXAFS analysis. Variable temperature EXAFS studies showed that  $\text{ReS}_4$  and  $\text{Re}_2\text{S}_7$  convert to  $\text{ReS}_2$  as anticipated from the results of TGA experiments. These considerations, when taken together with literature precedents, led to the reformulation of  $\text{Re}_2\text{S}_7$  as  $\text{Re}^{\text{V}}(\text{S})_{1.5}(\text{S}_2)_1$ , and correspondingly  $\text{ReS}_4$  is formulated as  $\text{Re}^{\text{V}}(\text{S})_1(\text{S}_2)_{1.5}$ . These two materials are proposed to be members of a continuum of  $\text{Re}(\text{S})_{1.5-1}(\text{S}_2)_{1-1.5}$  structures that differ in terms of their  $\text{S}_2^{2-}/\text{S}^{2-}$  ratio. Chain structures accommodate these considerations and are consistent with a largely reversible electrochemistry that regenerates  $\text{ReS}_4^-$ .

## Introduction

Transition metal sulfides (TMS) are immensely useful materials. The preponderate motivation for their study is associated with the utility of  $\text{MoS}_2$  and related materials as catalysts for the hydrodesulfurization (HDS) of petroleum.<sup>1,2</sup> TMS have also been exploited as candidates for secondary cathodes in batteries, technology that was commercialized in the case of the  $\text{Li}-\text{TiS}_2$  battery.<sup>3</sup> Beyond these practical considerations, the binary sulfides have attracted considerable interest for their novel electronic properties, e.g., charge density waves, quantum size effects, and superconductivity.<sup>4</sup> A recent theory on the origin of life invokes a key role played by  $\text{Fe}-\text{S}$  and  $\text{Fe}-\text{Ni}-\text{S}$  species.<sup>5,6</sup> Driven by the intense interest in TMS, new binary phases continue to be discovered and new synthetic techniques introduced.<sup>7-11</sup> In the preceding 20 years, several new TMS

materials have been described, including  $\text{TaS}_3$ ,<sup>12</sup>  $\text{Ta}_3\text{S}_2$ ,<sup>13</sup>  $\text{MoS}_{4.7}$ ,<sup>14</sup>  $\text{MoS}_{5.6}$ ,<sup>15</sup> and nanotubes of  $\text{MS}_2$  ( $\text{M} = \text{Ti}, \text{Mo}, \text{W}$ ).<sup>10,16,17</sup>

TMS can be classified according to their degree of sulfur-sulfur bonding. "Sulfur-rich" phases feature  $\text{S}-\text{S}$  bonding, usually in the form of persulfido units ( $\text{S}_2^{2-}$ ), the most famous example being  $\text{FeS}_2$ . Some species, illustrated by  $\text{TaS}_3$ , have both per- and monosulfido units. A second broad class of TMS includes materials with isolated sulfide ( $\text{S}^{2-}$ ) centers, e.g.,  $\text{MoS}_2$  and  $\text{FeS}$ . Metal-rich phases such as  $\text{Ta}_3\text{S}_2$  exhibit extensive metal-metal bonding.<sup>13</sup> Phases with low sulfur-metal ratios are generally more thermally stable than the sulfur-rich phases; thus, they are more amenable to high temperature recrystallization techniques. The sulfur-rich phases, on the other hand, are often thermally labile with respect to the loss of sulfur, e.g.,  $\text{MoS}_3$  and  $\text{Re}_2\text{S}_7$ . Because such species are not readily crystallized, they are often characterized by X-ray absorption spectroscopy (XAS), specifically extended X-ray absorption

\* Corresponding author.

<sup>†</sup> University of Illinois at Urbana-Champaign.

<sup>‡</sup> Yeshiva University.

<sup>§</sup> Brookhaven National Laboratory.

- (1) Pecoraro, T. A.; Chianelli, R. R. *J. Catal.* **1981**, *67*, 430–445.
- (2) Harris, S.; Chianelli, R. R. *J. Catal.* **1986**, *98*, 17–31.
- (3) Benco, L.; Barras, J.-L.; Atanasov, M.; Daul, C.; Deiss, E. *J. Solid State Chem.* **1999**, *145*, 503–510.
- (4) Jin, S.; Zhou, R.; Scheuer, E. M.; Adamchuk, J.; Rayburn, L. L.; DiSalvo, F. J. *Inorg. Chem.* **2001**, *40*, 2666–2674.
- (5) Huber, C.; Wächtershäuser, G. *Science* **1997**, *276*, 245–247.
- (6) Huber, C.; Wächtershäuser, G. *Science* **1998**, *281*, 670–672.
- (7) Gillan, E. G.; Kaner, R. B. *Chem. Mater.* **1996**, *8*, 333–343.
- (8) Ramli, E.; Rauchfuss, T. B.; Stern, C. L. *J. Am. Chem. Soc.* **1990**, *112*, 4044–4045.
- (9) Dusastre, V.; Omar, B.; Parkin, I. P.; Shaw, G. A. *J. Chem. Soc., Dalton Trans.* **1997**, *19*, 3505–3508.
- (10) Tenne, R. *Prog. Inorg. Chem.* **2001**, *50*, 269–315.

(11) Axtell, I. E.; Liao, J.-H.; Kanatzidis, M. G. *Inorg. Chem.* **1998**, *37*, 5583–5587.

(12) Meerschaut, A.; Guemas, L.; Rouxel, J. *J. Solid State Chem.* **1981**, *36*, 118–123.


(13) Kim, S. J.; Nanjundaswamy, K. S.; Hughbanks, T. *Inorg. Chem.* **1991**, *30*, 159–164.

(14) Hibble, S. J.; Rice, D. A.; Pickup, D. M.; Beer, M. P. *Inorg. Chem.* **1995**, *34*, 5109–5113.

(15) Afanasiev, P.; Bezverkhy, I. *Chem. Mater.* **2002**, *14*, 2826–2830.

(16) Feldman, Y.; Wasserman, E.; Srolovitz, D. J.; Tenne, R. *Science* **1995**, *267*, 222–225.

(17) Mastai, Y.; Homyonfer, M.; Gedanken, A.; Hodes, G. *Adv. Mater.* **1999**, *11*, 1010–1013.

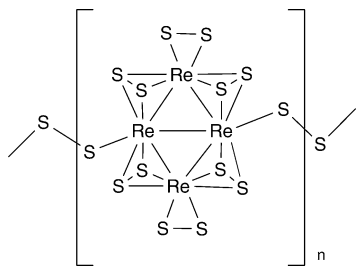

**Figure 1.** Structure proposed for  $\text{Re}_2\text{S}_7$  from initial EXAFS analyses.<sup>26,27</sup>

fine structure (EXAFS) and X-ray absorption near-edge structure (XANES).

The sulfides of  $\text{Re}^{18}$  have attracted recent attention because Re–S compositions are particularly active HDS and hydrogenation catalysts.<sup>19,20</sup> Single crystal X-ray diffraction has shown that  $\text{ReS}_2$  adopts a  $\text{CdCl}_2$  structure distorted by a Re–Re bonding network.<sup>21,22</sup> Interestingly,  $\text{ReS}_2$  obeys the 18e rule, when one includes the contributions of the localized Re–Re bonding. Beyond  $\text{ReS}_2$ , the only other generally accepted sulfide of rhenium is  $\text{Re}_2\text{S}_7$ , which has been used for the hydrogenation of difficult substrates that poison Pt metal catalysts, e.g., NO and  $\text{SO}_2$ .<sup>23</sup> A mineral identified as  $\text{ReS}_x$  ( $2 < x < 3$ ) has been reported but not characterized crystallographically.<sup>24</sup>

Dirhenium heptasulfide forms upon the acidification of solutions of the perthiorhenate ion  $\text{ReS}_4^-$  as well as by treatment of  $\text{Re}_2\text{O}_7$  with  $\text{H}_2\text{S}$ .<sup>25</sup> Hibble et al. have examined  $\text{Re}_2\text{S}_7$  by Re- and S-XANES and EXAFS.<sup>26,27</sup> These workers suggest that  $\text{Re}_2\text{S}_7$  consists of persulfido ligands exclusively, i.e.,  $\text{Re}_4(\text{S}_2)_7$  (Figure 1). Patterns in the structural chemistry of metal sulfides suggest that this structural proposal would be highly unusual. For example, the oxidation state of  $\text{Re}^{3.5+}$  is lower than even  $\text{ReS}_2$ . A reinvestigation of this material is reported herein.

The present project began with a study of the redox properties of  $\text{ReS}_4^-$ , whose metallo-organic chemistry we have recently described.<sup>28–31</sup> Schäfer et al. showed that  $\text{ReS}_4^-$  undergoes sequential reductions at  $-1.58$  and  $-2.46$  V vs  $\text{Fc}|\text{Fc}^+$ ,<sup>32</sup> and Ciurli et al. reported these

values as  $-1.12$  and  $-1.99$  V vs SCE.<sup>33</sup> The oxidation of  $\text{ReS}_4^-$  has not been previously explored, although we show here that it provides access to a novel sulfur-rich material.

## Experimental Section

**Materials and Methods.** Elemental analyses and thermogravimetric analysis (TGA) were conducted at the School of Chemical Sciences Microanalysis Laboratory. TGA measurements were performed on a Perkin-Elmer TGA7 and were conducted under an atmosphere of nitrogen or helium. Scanning electron microscopy (SEM) and X-ray energy dispersive spectroscopy (XEDS) were performed on a Zeiss DSM 960 at the Frederick Seitz Material Research Laboratory.  $\text{Et}_4\text{NReS}_4$  was prepared following our recent modification of a method described by Exxon.<sup>34</sup>  $\text{ReS}_2$  was purchased from Cerac and was examined by powder X-ray diffraction and inductively coupled plasma (ICP) elemental analysis. Anal. Calcd for  $\text{ReS}_2$  (found): Re, 74.38 (75.37); S, 25.62 (25.65). The manufacturer provided corroborating powder X-ray diffraction and elemental analysis data.  $\text{Re}_2\text{S}_7$  was purchased from Aldrich; powder X-ray diffraction analysis showed that this material was indeed amorphous. Anal. Calcd for  $\text{Re}_2\text{S}_7$  (Found): Re, 62.39 (62.01); S, 37.61 (35.40).

**Chemical Synthesis of  $\text{ReS}_4$  by  $\text{I}_2$  Oxidation.** A solution of 0.531 g (1.19 mmol) of  $\text{Et}_4\text{NReS}_4$  in 30 mL of MeCN was added dropwise to a solution of 0.093 g (0.733 mmol) of  $\text{I}_2$  in 30 mL of MeCN. A black precipitate formed immediately. The solid was collected by filtration and washed with MeCN and  $\text{Et}_2\text{O}$  and dried in vacuo. Yield: 0.22 g (60%). Anal. Calcd (Found) for  $\text{ReS}_4$ : C, 0 (5.25); H, 0 (0.88); N, 0 (1.07); Re, 55.39 (50.48). Attempts to remove the CHN impurities involved grinding the material in a  $\text{N}_2$  box followed by Soxhlet extraction in MeCN for 12 h which provided a material with a lower CHN content. Anal. Calcd (Found) for  $\text{ReS}_4$ : C, 0 (4.91); H, 0 (0.80); N, 0 (0.59); Re, 59.21 (54.40).

**Chemical Synthesis of  $\text{ReS}_4$  by  $\text{Fc}^+$  Oxidation.** A solution of 0.505 g (1.13 mmol) of  $\text{Et}_4\text{NReS}_4$  in 30 mL of MeCN was slowly added over 5 min to a solution 0.30 g (0.91 mmol) of  $(\text{Cp}_2\text{Fe})[\text{PF}_6]$  in 30 mL of MeCN. The resulting black precipitate was collected by filtration and washed with MeCN and  $\text{Et}_2\text{O}$  and dried in vacuo. Yield: 0.20 g (59%). Anal. Calcd (found) for  $\text{ReS}_4$ : C, 0 (3.75); H, 0 (0.37); N, 0 (0.38); Re, 55.39 (55.14). Attempts to remove the CHN impurities involved grinding the material in a  $\text{N}_2$  box followed by Soxhlet extraction with MeCN for 12 h, which provided a material with a lower CHN content. Anal. Calcd (Found) for  $\text{ReS}_4$ : C, 0 (3.06); H, 0 (0.36); N, 0 (0.0); Re, 59.21 (55.24).

**Electrochemical Synthesis of  $\text{ReS}_4$ .** The cyclic voltammetry experiments were performed with a Bioanalytical System BAS-CV 50W electrochemical analyzer in an  $\text{N}_2$ -purged 10 mL single compartment glass cell. The working electrode was either glassy carbon or Pt foil. The reference electrode was a  $\text{Ag}|\text{AgCl}$ , KCl (satd) electrode, and the counter electrode was Pt wire.

In one experiment, a stirred 4 mM solution of  $\text{Et}_4\text{NReS}_4$  in 8 mL of MeCN (0.1 M  $\text{Bu}_4\text{NPF}_6$ ) was maintained at 0.6 V vs  $\text{Ag}|\text{AgCl}$  for 2 min. After this time, a black coating had accumulated on the Pt electrode. The reversibility of the electrodeposition was demonstrated by removing the coated electrode and rinsing it in air with MeCN, inserting the electrode into a fresh MeCN solution (0.1 M  $\text{Bu}_4\text{NPF}_6$ ), and applying a potential of  $-900$  mV which resulted in the black layer dissolving over 30 s and providing a faint purple solution. The presence of  $\text{ReS}_4^-$  in solution was confirmed by UV–vis spectroscopy ( $\lambda_{\text{max}} = 508$  nm).

Bulk electrochemical synthesis was performed in a 100 mL cell with a piece of 2  $\text{cm}^2$  Pt foil as the working electrode. The

(18) Saito, T. *J. Chem. Soc., Dalton Trans.* **1999**, 97–105.

(19) Stiefel, E. I. *ACS Symp. Ser.* **1996**, 653, 2–38.

(20) Topsøe, H.; Clausen, B. S.; Massoth, F. E. *Hydrotreating Catalysis, Science and Technology*; Springer-Verlag: Berlin, 1996.

(21) Kelty, S. P.; Ruppert, A. F.; Chianelli, R. R.; Ren, J.; Whangbo, M. H. *J. Am. Chem. Soc.* **1994**, 116, 7857–7863.

(22) Murray, H. H.; Kelty, S. P.; Chianelli, R. R.; Day, C. S. *Inorg. Chem.* **1994**, 33, 4418–4420.

(23) Slaughter, L. H. *Inorg. Chem.* **1964**, 3, 920–921.

(24) Korzhinsky, M. A.; Tkaschenko, S. I.; Schmulovich, K. I.; Taran, Y. A.; Steinberg, G. S. *Nature* **1994**, 369, 51–52.

(25) Briscoe, H. V. A.; Robinson, P. L.; Stoddart, E. M. *J. Chem. Soc.* **1931**, 1439–1443.

(26) Hibble, S. J.; Walton, R. I.; Feaviour, M. R.; Smith, A. D. *J. Chem. Soc., Dalton Trans.* **1999**, 2877–2883.

(27) Hibble, S. J.; Walton, R. I. *J. Chem. Soc., Chem. Commun.* **1996**, 2135–2136.

(28) Goodman, J. T.; Inomata, S.; Rauchfuss, T. B. *J. Am. Chem. Soc.* **1996**, 118, 11674–11675.

(29) Goodman, J. T.; Rauchfuss, T. B. *Angew. Chem., Int. Ed. Engl.* **1997**, 36, 2083–2085.

(30) Goodman, J. T.; Rauchfuss, T. B. *Inorg. Chem.* **1998**, 37, 5040–5041.

(31) Goodman, J. T.; Rauchfuss, T. B. *J. Am. Chem. Soc.* **1999**, 121, 5017–5022.

(32) Schäfer, R.; Kaim, W.; Moscherosch, M.; Krejci, M. *J. Chem. Soc., Chem. Commun.* **1992**, 834–835.

(33) Ciurli, S.; Carney, M. J.; Holm, R. H.; Papaefthymiou, G. C. *Inorg. Chem.* **1989**, 28, 2696–2698.

(34) Goodman, J. T.; Rauchfuss, T. B. *Inorg. Synth.* **2002**, 33, 107–110.

saturated solution of  $\text{Et}_4\text{NReS}_4$  in MeCN (0.1 M  $\text{Bu}_4\text{NPF}_6$ ) was held at 0.6 V vs  $\text{Ag}|\text{AgCl}$  for 100 s. The electrode was then removed and washed with MeCN and dried in air. The black material was removed from the electrode with a razor blade and thoroughly dried in vacuo overnight. Analysis by XEDS confirmed the Re/S ratio of 1:4. Found (Theory): Re, 59.51 (59.21); S, 40.49 (40.79). XEDS over several parts of the sample confirmed its uniformity. IR analysis in the 4000–700  $\text{cm}^{-1}$  range showed no prominent absorptions.

**Samples for XAS.** Samples for XAS analysis were ground in a  $\text{N}_2$  atmosphere and passed through a 200 mesh sieve. The powder was then mixed thoroughly with an equal weight of carbon black. About 25 mg of the mixture was pressed into a rectangular wafer using a hydraulic press. The wafers were approximately 0.5 mm thick, thereby satisfying the condition that  $\Delta\mu x \leq 1$ , where  $x$  is the effective sample thickness and  $\Delta\mu$  is the jump in absorption coefficient at the Re  $L_{\text{III}}$  absorption edge (10 534 eV). The samples were then mounted on the vertical stage in a custom-built variable temperature cell,<sup>35,36</sup> which is suited for simultaneous in situ X-ray fluorescence and transmission measurements. The in-situ cell was purged with helium for >1 h prior to heating the samples. Elevated temperature measurements were conducted under a flowing helium atmosphere. The temperature was monitored with a chromel/alumel thermocouple (Omega) attached directly to the sample mounting stage. The sample was allowed to equilibrate for a minimum of 1 h at each temperature prior to data collection. Acetonitrile solutions of  $\text{Et}_4\text{NReS}_4$  were studied only at room temperature and under argon in a custom-designed liquid sample cell with an exposed solution volume of 0.25 mL (dimensions 25 × 5 × 2 mm<sup>3</sup>).

**XAS Measurements.** The EXAFS measurements were obtained at the beamline X16C of the National Synchrotron Light Source (Brookhaven National Laboratory, Upton, NY). The X16C beamline uses a sagittally focusing double-crystal monochromator with Si(111) crystals which focus 3.5 mrad of light into a 0.3 × 0.5 mm<sup>2</sup> beam spot at the sample. The intensity of the focused beam ( $I_0$ ) was measured with a 15 cm long ion chamber filled with a 10:1 mixture of He/Ar. X-ray absorption data from the sample were measured primarily in transmission mode by scanning from 200 eV below to 1000 eV above the Re  $L_{\text{III}}$  edge. A 30 cm long Ar-filled ion chamber placed after the sample, collinear with the beam, was used to measure the transmission beam intensity,  $I_t$ . The  $\text{Et}_4\text{NReS}_4$  solution X-ray absorption data was measured in both transmission and fluorescence modes. This was accomplished by turning the solution cell containing the sample to ~45° with respect to the beam direction and measuring the intensity of the transmitted ( $I_t$ ) X-rays and the intensity of the X-ray fluorescence ( $I_f$ ) from the sample. A 4 cm long, Ar-filled ion chamber (Lytle detector) placed at 90° with respect to the beam direction was used to measure  $I_f$ . A standard, thin Re metal foil was used to calibrate the beam energy during each Re  $L_{\text{III}}$ -edge XAS scan for all samples. The calibration measurement was made with the reference ion chamber ( $I_r$ ) placed downstream of  $I_t$ . The measurements of the absorption coefficient near the Re  $L_{\text{III}}$  edge in pure Re were taken simultaneously with the samples of interest by placing the Re metal standard between the ion chambers  $I_t$  and  $I_r$ , and measuring the absorption coefficient in  $I_r$  due to the metal standard. The characteristic features of the absorption coefficient in pure Re were later used to accurately calibrate (0.3 eV or better) the X-ray energy of each scan.

In situ temperature measurements were performed by heating the sample with a resistor heater while flowing He gas at 40 mL/min over the sample. The setup and experimental conditions, overall, were very similar to other in situ reaction measurements performed at this beamline during the recent years.<sup>36–38</sup>

**EXAFS Data Analysis.** Our analysis procedure was tested on  $\text{ReS}_2$  and  $\text{Et}_4\text{NReS}_4$ ; both of these compounds have been structurally characterized by single crystal X-ray diffraction (see Introduction) and thus are suitable reference compounds. The ion  $\text{ReS}_4^-$  is a molecular species and therefore quite different from  $\text{ReS}_4$ , which is expected to be a structurally complex extended solid. The structural model for  $\text{ReS}_2$  was constructed using the coordinates from Murray et al.'s crystallographic study,<sup>22</sup> which contains two inequivalent Re sites in the unit cell, each octahedrally coordinated by sulfur atoms. The Re–S bond lengths in  $\text{ReS}_2$  range from 2.31 to 2.50 Å, the average length being 2.40 Å. For each Re site, the six nearest Re–Re neighbors are divided into two groups with respect to their lengths, three in each group. These Re–Re lengths fall into two distinct ranges, one group of three Re–Re pairs (from 2.69 to 2.90 Å) is centered around 2.80 Å, and the second group of three Re–Re pairs (from 3.56 to 3.77 Å) is centered around 3.68 Å. This variety of bond lengths is a result of the sulfur being situated above or below three, two, one, or zero Re–Re bonds. For our fitting procedure, the Re–S interactions were modeled theoretically using FEFF6,<sup>39</sup> using calculations based on the atomic coordinates of the  $\text{ReS}_2$  structure. A theoretical, 6-fold degenerate Re–S contribution to the first shell, with the bond length of 2.40 Å, was calculated and chosen to simulate the entire Re–S shell by varying the correction to the model bond length, the mean square bond lengths disorder ( $\sigma^2$ ), and the coordination number of the pair. Similarly, two theoretical contributions were constructed with FEFF6 for two groups of Re–Re distances. To fit more Re–Re contributions to the EXAFS data, their bond lengths, disorder, and coordination numbers were varied in the fits as well. To analyze the data with FEFF theory, we used the UWEXAFS<sup>40</sup> data analysis package (programs AUTOBK and FEFFIT) that utilizes the nonlinear least-squares fitting of EXAFS theory to the data and evaluates the uncertainties in the results.

## Results

**Electrochemistry of  $\text{ReS}_4$ .** Using cyclic voltammetry, we confirmed the previously reported  $\text{ReS}_4^{-2/2-}$  couple at –1120 mV (vs SCE, Figure 2).<sup>33</sup> In the anodic scan direction, we observed a previously unreported oxidation wave at 0.5 V. This irreversible oxidation process is coupled to a (reductive) stripping peak at –0.9 V. The stripping peak was not observed unless the potential was first swept to  $\geq 0.5$  V. If, however, the oxidation of  $\text{ReS}_4^-$  was taken to very positive potentials, a large event is observed at 1.6 V, and the stripping peak at –0.9 V was no longer observed.

The electrodeposition proved to be reasonably reversible. In a typical reaction, the coated electrode could be removed from the electrolyte solution, rinsed with MeCN, and re-reduced at –900 mV in a fresh electrolyte solution to cleanly regenerate  $\text{ReS}_4^-$ , which was confirmed by optical measurements. In a coulometry experiment, an 8 mM solution of  $\text{Et}_4\text{NReS}_4$  in MeCN was first swept from –100 to 700 mV (25  $\text{mV}\cdot\text{s}^{-1}$ ), and the second segment swept from 700 to –1500 mV. Under these conditions,  $-1.58 \times 10^{-4}$  C and  $9.92 \times 10^{-5}$  C were transferred, respectively, for a stripping efficiency of 63%. The deviation from unity can be partially attributed to delamination of the deposited  $\text{ReS}_4$  material from the electrode.

(37) Rodriguez, J. A.; Hanson, J. C.; Frenkel, A. I.; Kim, J. Y.; Perez, M. J. *Am. Chem. Soc.* **2002**, *124*, 346–354.


(38) Frenkel, A. I.; Hills, C. W.; Nuzzo, R. G. *J. Phys. Chem. B* **2001**, *105*, 12689–12703.

(39) Zabinsky, S. I.; Rehr, J. J.; Aukudinov, A.; Albers, R. C.; Eller, M. J. *Phys. Rev. B: Condens. Matter* **1995**, *52*, 2995–3009.

(40) Stern, E. A.; Newville, M.; Ravel, B.; Yacoby, Y.; Haskell, D. *Physica B (Amsterdam)* **1995**, *208–209*, 117–120.

(35) Nashner, M. S.; Frenkel, A. I.; Adler, D. L.; Shapley, J. R.; Nuzzo, R. G. *J. Am. Chem. Soc.* **1997**, *119*, 7760–7771.

(36) Nashner, M. S.; Frenkel, A. I.; Somerville, D.; Hills, C. W.; Shapley, J. R.; Nuzzo, R. G. *J. Am. Chem. Soc.* **1998**, *120*, 8093–8101.

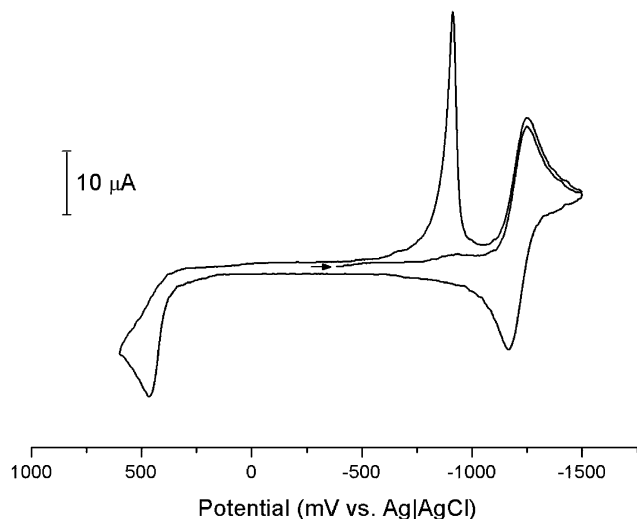

**Figure 2.** Cyclic voltammogram of 0.6 mM solution of  $\text{Et}_4\text{NReS}_4$  in MeCN (0.1 M  $\text{Bu}_4\text{NPF}_6$ ). The sweep rate was 100 mV/s.

**Bulk Preparation of  $\text{ReS}_4$ .** Prolonged oxidation of MeCN solutions of  $\text{Et}_4\text{NReS}_4$  at 0.5 V in a stirred solution produced a thick black deposit on the working electrode (Pt foil). This solid, which was easily removed by scraping, proved to be amorphous on the basis of X-ray powder diffraction measurements. XEDS measurements showed that the solid retained its Re/S ratio of 1:4.

We also generated  $\text{ReS}_4$  via chemical methods. Both  $\text{I}_2$  and  $[\text{Cp}_2\text{Fe}]\text{PF}_6$  effect the oxidation, consistent with their redox potentials of 0.75 and 0.5 V vs  $\text{Ag}|\text{AgCl}$ , respectively. We intentionally employed a deficiency of oxidants in order to minimize entrainment of impurities in the resulting solid; the electrochemically synthesized material was of higher purity. Elemental analysis indicated that the chemically produced material contained 10–15% CHN, probably occluded  $\text{Et}_4\text{NI}$  or  $\text{Cp}_2\text{-Fe}$ . Soxhlet extraction of these solids with MeCN reduced the level of impurities to 3–5%.

**Re  $L_{III}$ -Edge EXAFS.** Given the amorphous nature of  $\text{ReS}_4$ , we turned to XAS measurements to obtain structural information on this material.  $\text{ReS}_2$ ,  $\text{Re}_2\text{S}_7$ , and  $\text{ReS}_4$  (synthesized by  $\text{Fc}^+$  and electrochemical oxidation) were analyzed using nearly identical conditions. Data for  $\text{Et}_4\text{NReS}_4$  were measured in an MeCN solution by both transmission and fluorescence modes.

Our EXAFS data for  $\text{ReS}_2$  was satisfactorily fit using only three contributors (single scattering paths) to the EXAFS: six Re–S paths of half path lengths (the interatomic distances) of 2.40 Å, three Re–Re paths at 2.82 Å, and three Re–Re paths at 3.70 Å. Because the structure of  $\text{ReS}_2$  is known, we did not vary coordination numbers in the fits. Our fits were good for EXAFS distances  $< 3$  Å, where two nearest neighboring shells contributed to the data (six Re–S pairs and the first group of three Re–Re pairs). The misfit in the higher  $r$  range is caused by our neglecting further neighbors, i.e., ones lying beyond the Re–Re shell. As a consequence, we do not analyze the data for contributors residing  $> 3$  Å in  $r$ -space. We do, however, include the second Re–Re group to fit  $\text{ReS}_2$  data, in order to improve the quality of the fit in the low  $r$  region.

We have fixed the coordination numbers of Re–S and Re–Re contributions in the  $\text{ReS}_2$  fits as 6 and 3,

**Table 1. Comparison of Distances and Coordination Numbers (CN) for  $\text{ReS}_2$  Deduced from Crystallographic,<sup>22</sup> EXAFS from Hibble et al.,<sup>27</sup> and the Present EXAFS Data**

	Re–S [Å]	Re–Re [Å]	CN (Re–S)	CN (Re–Re)	$\sigma^2$ (Re–S) [Å <sup>2</sup> ]	$\sigma^2$ (Re–Re) [Å <sup>2</sup> ]
XRD	2.3976	2.803	6	3		
Hibble	2.362(2)	2.759(3)	6.0(2)	3.2(5)	0.0134(5)	0.015(1)
this work	2.389(7)	2.81(1)	6 <sup>a</sup>	3 <sup>a</sup>	0.0059(4)	0.007(1)

<sup>a</sup> CN values in EXAFS fits were fixed to be those from the XRD measurements.

**Table 2. Comparison of EXAFS Data for  $\text{Re}_2\text{S}_7$**

	Re–S [Å]	Re–Re [Å]	CN (Re–S)	CN (Re–Re)	$\sigma^2$ (Re–S) [Å <sup>2</sup> ]	$\sigma^2$ (Re–Re) [Å <sup>2</sup> ]
Hibble <sup>27</sup>	2.325(2)	2.739(3)	5.0(2)	2.8(4)	0.0182(7)	0.0156(1)
this work	2.354(7)	2.76(1)	5.6(7)	1.7(5)	0.009(2)	0.006(3)

respectively, in agreement with the crystallography, in order to find the best fit value of the passive electron reduction factor ( $S_0^2 = 0.80(4)$ ) that correlates with coordination numbers.  $S_0^2$  was subsequently fixed equal to 0.80 for the rest of the EXAFS data fits where the coordination numbers were varied.

Our analyses, and that from Hibble et al.<sup>27</sup> for  $\text{ReS}_2$ , were based on previously published crystallographic coordinates.<sup>22</sup> The interatomic distances deduced in each of these studies are presented in Table 1; the results from this study are in slightly better agreement with the crystallographically determined distances than those reported by Hibble.

The  $\text{ReS}_2$  data analysis was performed by using  $k^2$ -weighting to obtain both Re–S and Re–Re distances by simultaneously fitting FEFF theories of these pairs to the EXAFS data in  $r$ -space. This procedure was successful due to the relatively small number of fitting parameters. However, in the samples with unknown number of neighbors of each type, the difference in backscattering amplitudes  $f(k)$  of Re–S and Re–Re photoelectron paths complicates the analysis. Namely,  $f(k)$  for Re–S path contributes more strongly to the shorter  $k$ -range of the EXAFS data than that for Re–Re path, since Re is a stronger scatterer than S. We obtained better results by emphasizing the contribution of each bonding pair by using different  $k^n$ -weightings ( $k^2$  or  $k^3$ ) to fit Re–S and Re–Re contributions, respectively. We first used  $k^2$ -weighting to Fourier transform both EXAFS data and FEFF theory in order to refine the Re–S contribution to the data that affects the lower  $k$ -range stronger than Re–Re contribution. In this round of the analysis, we fit both theoretical contributions, Re–S and Re–Re, to the data simultaneously, using the  $r$ -range from 1.6 to 3.1 Å. Second, we subtracted theoretical Re–S contribution from the data and analyzed the resultant differential signal by fitting the Re–Re contribution in  $r$ -range from 2 to 3.2 Å using  $k^3$ -weighting for both the data and FEFF theory to further suppress any unsubtracted Re–S contributions and emphasize Re–Re contributions. The results are summarized in the Tables 1–5. The EXAFS data and fits are displayed in Figures 3–5. A similar analysis protocol has been used successfully to analyze separately the Nb–Nb and Nb–O contributions to the structure of  $\text{KNbO}_3$ , a material whose EXAFS data suffers from the same problem as described above.<sup>41</sup>

A sample of  $\text{Et}_4\text{NReS}_4$  was measured as a MeCN solution by fluorescence EXAFS. These data were fit

**Table 3. Comparison of Bond Lengths ( $\text{\AA}$ ) and Coordination Numbers (CN) between  $\text{ReS}_2$  and the Decomposition Products of  $\text{Re}_2\text{S}_7$  and  $\text{ReS}_4$  at 723 K**

	Re-S [ $\text{\AA}$ ]	Re-Re [ $\text{\AA}$ ]	CN (Re-S)	CN (Re-Re)	$\sigma^2$ (Re-S) [ $\text{\AA}^2$ ]	$\sigma^2$ (Re-Re) [ $\text{\AA}^2$ ]
$\text{ReS}_2$	2.38(1)	2.80(3)	6	3	0.0076(7)	0.009(3)
$\text{Re}_2\text{S}_7$	2.379(7)	2.76(1)	6.3(5)	2.6(5)	0.009(1)	0.010(2)
$\text{ReS}_4$	2.379(7)	2.81(3)	5.7(3)	1.7(1.5)	0.0077(7)	0.010(4)

**Table 4. EXAFS Data for  $\text{Re}_2\text{S}_7$  and Its Decomposition Products at 300, 473, 598, and 723 K**

	300 K	473 K	598 K	723 K
Re-S [ $\text{\AA}$ ]	2.354(7)	2.35(1)	2.34(1)	2.379(7)
Re-Re [ $\text{\AA}$ ]	2.76(1)	2.759(9)	2.75(1)	2.76(1)
CN (Re-S)	5.6(7)	5.2(5)	6.1(6)	6.3(5)
CN (Re-Re)	1.7(5)	1.4(2)	3.5(8)	2.6(5)
$\sigma^2$ (Re-S) [ $\text{\AA}^2$ ]	0.009(2)	0.008(1)	0.009(1)	0.007(6)
$\sigma^2$ (Re-Re) [ $\text{\AA}^2$ ]	0.006(3)	0.004(1)	0.008(2)	0.010(2)

using the Re-S path only. From the best fit, we determined the Re-S distance to be 2.13(1)  $\text{\AA}$  and a Re-S coordination number of 3.5(7). The actual bond distance as determined by single crystal X-ray crystallography averages to 2.126(5)  $\text{\AA}$ .<sup>42</sup> Note that the model correctly predicted the bond distance even though there are no Re=S bonds in  $\text{ReS}_2$ .

Our Re L<sub>III</sub>-edge results on  $\text{Re}_2\text{S}_7$  and  $\text{ReS}_4$ , together with data previously reported by Hibble et al. on  $\text{Re}_2\text{S}_7$ , are shown in Table 2. Regarding  $\text{Re}_2\text{S}_7$ , the Re-Re and Re-S bond distances determined by us are close to those previously reported. The occurrence of terminal Re=S bonds was ruled out. In particular, our model excludes such short Re-S bonds (ca. 2.15  $\text{\AA}$ <sup>33</sup>) because the resulting  $\sigma^2$  would be quite large ( $\sim 0.15 \text{\AA}^2$ ). A unimodal distribution of Re-S bond lengths, as opposed to a bimodal one, is the only scenario consistent with experimental observations.


Our analysis suggested fewer Re-Re pairs (1.7(5) vs 2.8(4)) than previously reported. In this context it is important to note that in our work we were able to emphasize the contribution of Re-Re bonds to the total EXAFS spectrum by  $k^3$ -weighting procedure. This two-step fitting procedure leads to a more reliable set of coordination numbers and distances than the one-step fitting process adopted in the earlier work. The reliability of the analysis was indicated by the close similarity of the data obtained for pristine  $\text{ReS}_2$  and a sample of the same derived by thermal decomposition of  $\text{Re}_2\text{S}_7$  at 723 K (see below).

**Sulfur K-Edge XANES Measurements.** Sulfur K-edge XANES spectra provide characteristic "fingerprint" information on the redox state of the sulfur because of the sensitivity of XANES to the oxidation state of sulfur and its electronic environment.<sup>43-45</sup> The energy position of the main XANES peak, which represents a core-level s-p transition, shifts by about 1.25


**Table 5. EXAFS Data for  $\text{ReS}_4$  and Its Decomposition Products at 300, 373, 473, 543, 573, 673, and 723 K**

	300 K	373 K	473 K	543 K	573 K	673 K	723 K
Re-S [ $\text{\AA}$ ]	2.34(2)	2.34(2)	2.366(7)	2.36(1)	2.35(1)	2.371(9)	2.379(7)
Re-Re [ $\text{\AA}$ ]	2.77(1)	2.75(1)	2.779(7)	2.77(1)	2.787(6)	NA <sup>a</sup>	2.81(3)
CN Re-S	4.6(6)	4.6(7)	6.2(5)	6.8(1.2)	6.2(7)	5.3(8)	5.7(3)
CN Re-Re	2.8(5)	3.9(9)	2.3(3)	3.6(6)	2.6(3)	NA <sup>a</sup>	1.7(1.5)
$\sigma^2$ (Re-S) [ $\text{\AA}^2$ ]	0.006(2)	0.007(2)	0.008(1)	0.011(3)	0.009(2)	0.006(2)	0.0077(7)
$\sigma^2$ (Re-Re) [ $\text{\AA}^2$ ]	0.006(1)	0.010(2)	0.006(2)	0.008(2)	0.009(1)	NA <sup>a</sup>	0.010(4)

<sup>a</sup> High noise level in some high-temperature data prevented analysis. <sup>b</sup>  $\text{Re-Re}$  coordination is the oxidation of sulfur, i.e., ca.

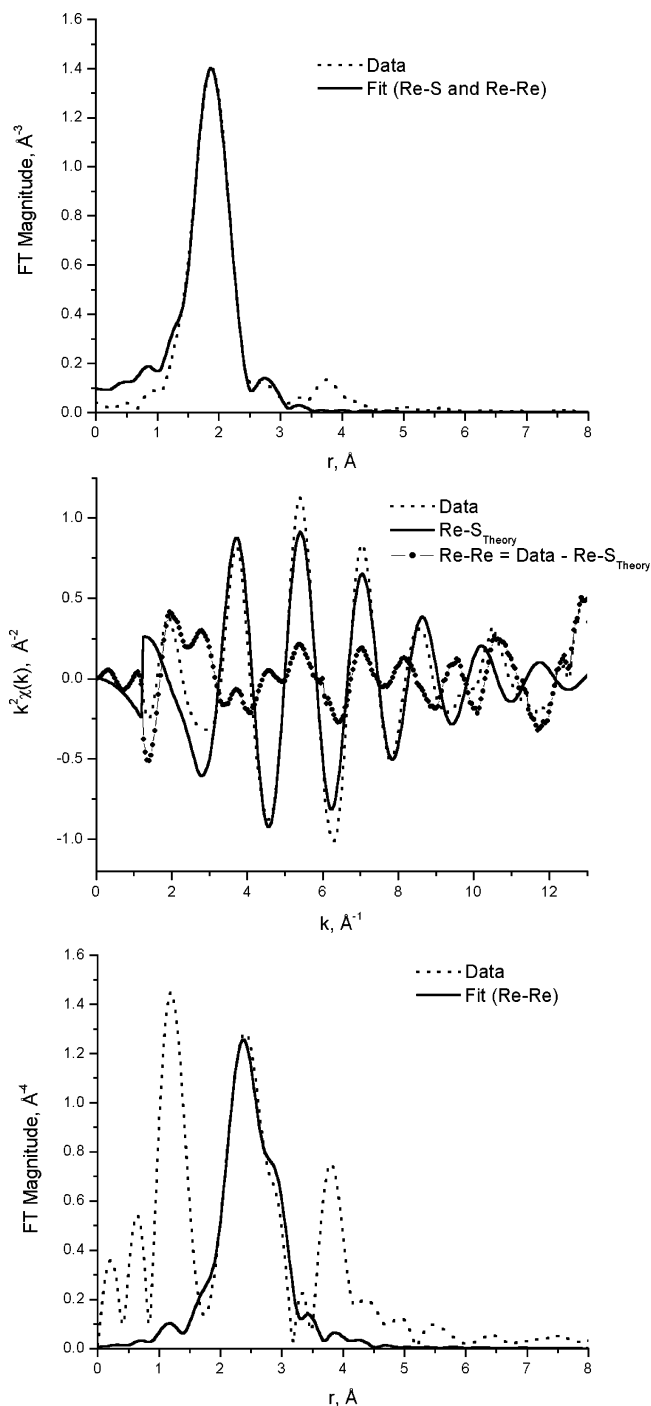

**Figure 3.** EXAFS fit for the Re-S and Re-Re shells (between 1.6 and 3.1  $\text{\AA}$ ), using  $k^2$ -weighting and  $k$ -range from 2 to 10  $\text{\AA}^{-1}$  for both theory and the data for  $\text{Re}_2\text{S}_7$  at 300 K (top), the subtraction of the best fit theory for the Re-S shell from the data (middle), and the fit to the remaining Re-Re shell (between 2 and 3.2  $\text{\AA}$ ) using  $k^3$ -weightings and  $k$ -range from 2 to 9  $\text{\AA}^{-1}$  (bottom). The mismatch between the theory and the data below 1.6  $\text{\AA}$  in the top and bottom panes is off the fitting range and is an artifact of background removal.

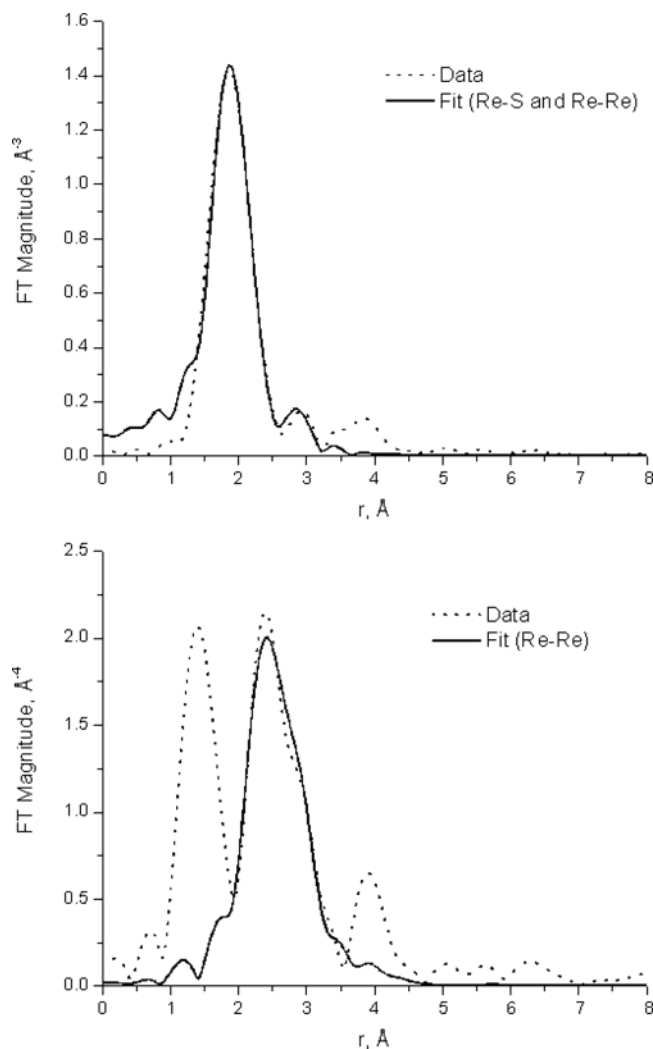

**Figure 4.** EXAFS fits for the Re–S and Re–Re shells for  $\text{ReS}_4$  at 300 K using  $k^2$ -weighting for the Re–S and Re–Re shells fitting between 1.6 and 3.1 Å and the  $k$ -range from 2 to 10  $\text{Å}^{-1}$  (top), subtracting the best-fit theory of the Re–S shell from the data and then fitting the residual with Re–Re contribution only between 2 and 3.2 Å, using  $k^3$ -weighting and  $k$ -range from 3 to 10  $\text{Å}^{-1}$  (bottom).

10 eV difference between sulfide (2471.3 eV for  $\text{FeS}$ ) and sulfate (2483.1 eV for  $\text{Na}_2\text{SO}_4$ ). In addition to  $\text{ReS}_4$  and  $\text{Re}_2\text{S}_7$ , the standards  $\text{FeS}$ ,  $\text{FeS}_2$ , and  $\text{Na}_2\text{SO}_4$  were also analyzed.

Our results showed similar XANES spectra for  $\text{ReS}_4$  and  $\text{Re}_2\text{S}_7$ , consistent with the presence of similar sulfur ligands in these materials. The main peak at 2472.7 eV is consistent with persulfide ( $\text{S}^-$ ) sulfur. Furthermore, both spectra show a shoulder that becomes evident upon deconvolution (Figure 6).<sup>45</sup> This shoulder function was fit with peak at 2471.1 eV, which is in the range expected for  $\text{S}^{2-}$ . The relative intensities of the two peaks indicate the  $\text{S}^-/\text{S}^{2-}$  ratios of ca. 3.5:1.6 for  $\text{Re}_2\text{S}_7$  and 3.5:1.8 for  $\text{ReS}_4$ . In addition to the main peaks, several other peak functions are required to fit the XANES spectra completely. These include an arctangent function representing electronic transition to the continuum and several nonspecific localized electronic transitions.<sup>45</sup> Elemental sulfur ( $\text{S}^0$ ), which has a characteristic peak near 2473.1 eV, was not observed.

**Variable Temperature Measurements.** TGA measurements on  $\text{ReS}_4$  revealed a major loss of weight at

$\sim 523$  K followed by a more gradual loss up to 1073 K. The net weight loss corresponded to 26%. The weight loss calculated for the conversion of  $\text{ReS}_4$  into  $\text{ReS}_2$  is 20.4%. Our sample contained  $\sim 5\%$  CHN; therefore, the total weight loss was anticipated to be 25.4%. The TGA for  $\text{Re}_2\text{S}_7$  showed a weight loss of 22% over the range 385–535 K, corresponding to the conversion of  $\text{Re}_2\text{S}_7$  to  $\text{ReS}_2$ .<sup>46</sup>

EXAFS measurements were conducted on a sample of  $\text{Re}_2\text{S}_7$  as a function of temperature from 300 to 723 K (Table 4). Our EXAFS measurements indeed show the conversion of  $\text{Re}_2\text{S}_7$  into a material with the bond lengths and coordination numbers similar to those found in  $\text{ReS}_2$  (Tables 3 and 4).

EXAFS measurements were also made on a sample of  $\text{ReS}_4$  and its decomposition products as a function of temperature from 300 to 723 K (Table 5).

The Re  $L_{\text{III}}$  edge EXAFS for  $\text{ReS}_4$  shows prominent features at  $\sim 2$  and 3 Å due to the Re–S and Re–Re coordination shells, respectively. These data were analyzed at each temperature using protocols as were employed for  $\text{Re}_2\text{S}_7$  data analysis. Both sets of data indicated that upon heating, both  $\text{Re}_2\text{S}_7$  and  $\text{ReS}_4$  material converted to  $\text{ReS}_2$ , consistent with the TGA data (Table 3).

We do not rule out the possibility that the Re–S coordination number is underestimated in  $\text{ReS}_4$  and correspondingly its  $\sigma^2$  is overestimated (Table 5), at the lower measurement temperatures since these quantities can be correlated in the fitting procedures. One reason to suspect an underestimation of the ReS CN is that the otherwise similar compound,  $\text{Re}_2\text{S}_7$ , has a Re–S coordination number larger and smaller  $\sigma^2$  (Table 4) than those found in  $\text{ReS}_4$  (Table 5).

## Discussion

This report describes the characterization of one of two known rhenium sulfur phases,  $\text{Re}_2\text{S}_7$ , and the synthesis and structural characterization of the new phase  $\text{ReS}_4$ .

**Synthesis.** The electropolymerization of a binary metal sulfide is a reaction that is without precedence, although electrochemical methods have been employed with some success in the synthesis of other sulfur-rich TMS.<sup>47</sup> Perhaps most unusual is the noted facility of the reductive depolymerization of  $\text{ReS}_4$ ; this behavior has not been observed previously for other metal sulfide phases. The large gap between the deposition and the re-reduction (stripping) potentials for  $\text{ReS}_4$  suggests that the polymerization entails a substantial structural rearrangement, a finding that is in turn consistent with the XAS results. As has been discussed extensively

(41) Frenkel, A. I.; Wang, F. M.; Kelly, S.; Ingalls, R.; Haskel, D.; Stern, E. A.; Yacoby, Y. *Phys. Rev. B: Condens. Matter* **1997**, *56*, 10869–10877.

(42) Müller, A.; Krickemeyer, E.; Bögge, H. *Z. Anorg. Allg. Chem.* **1987**, *554*, 61–78.


(43) Pickering, I. J.; Prince, R. C.; Divers, T.; George, G. N. *FEBS Lett.* **1998**, *441*, 11–14.

(44) Vairavamurthy, A.; Manowitz, B.; Zhou, W.; Jeon, Y. *ACS Symp. Ser.* **1994**, *550*, 412–430.

(45) Vairavamurthy, A. *Spectrochim. Acta, Part A* **1998**, *54A*, 2009–2017.

(46) Nirsha, B. M.; Savel'eva, L. V.; Rekharskii, V. I. *Izv. Akad. Nauk SSSR, Neorg. Mater.* **1984**, *20*, 164–165.

(47) Bélanger, D.; Laperriere, G.; Marsan, B. *J. Electroanal. Chem.* **1993**, *347*, 165–183.

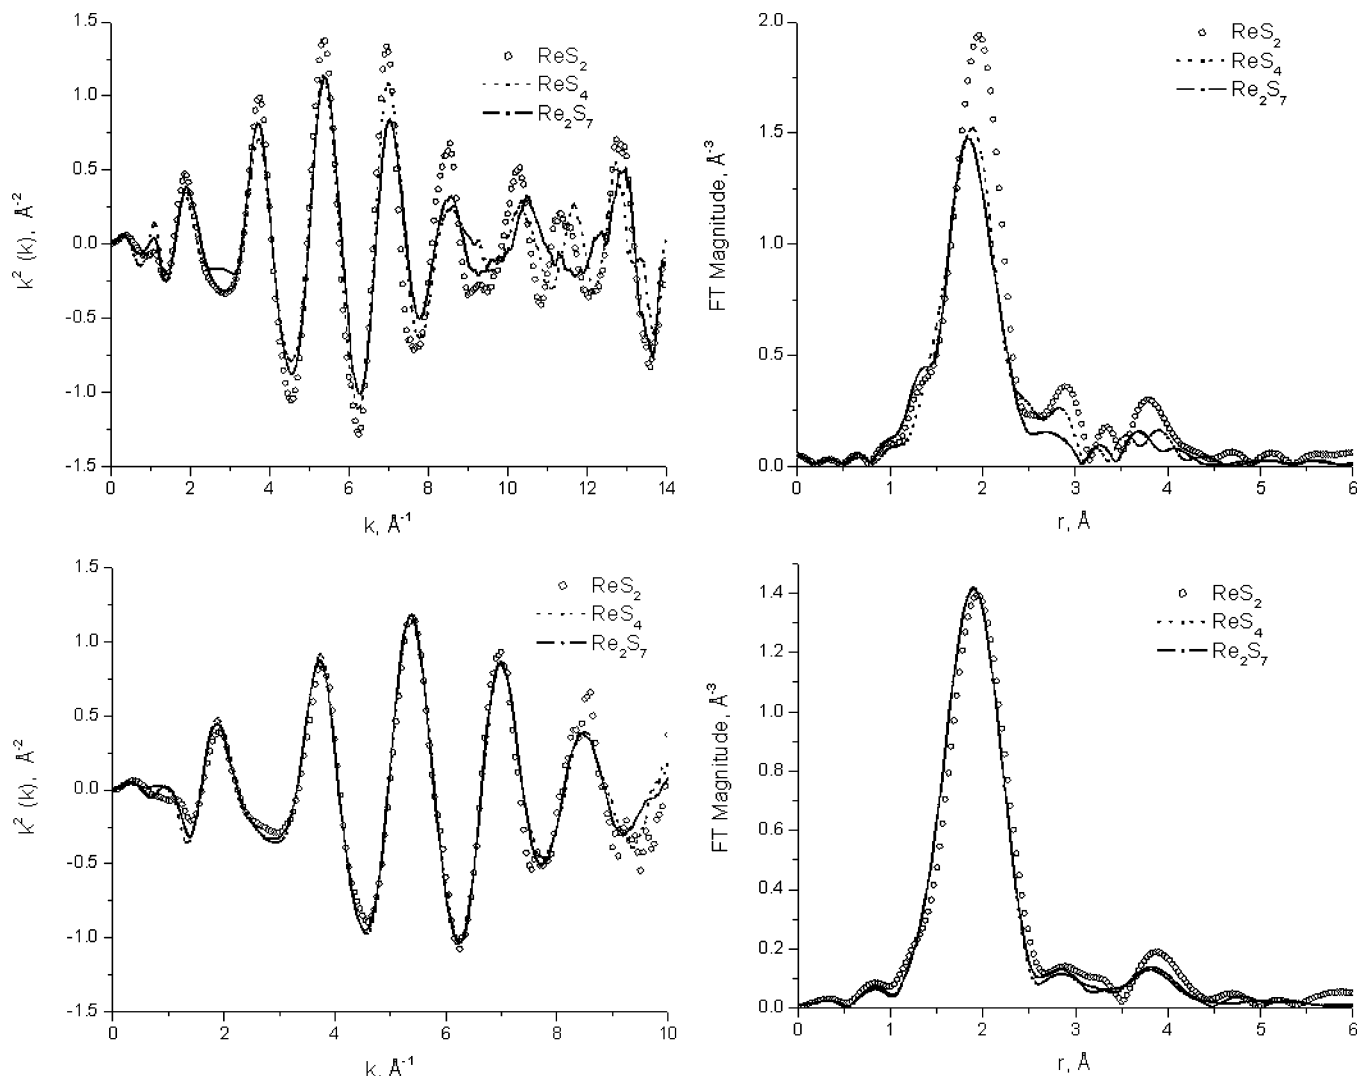

**Figure 5.** EXAFS data for the Re–S shell at 300 K for  $\text{ReS}_4$ ,  $\text{Re}_2\text{S}_7$ , and  $\text{ReS}_2$  (top row) and 700 K for  $\text{ReS}_2$  and the decomposition products of  $\text{ReS}_4$  and  $\text{Re}_2\text{S}_7$  (bottom row).  $k^2$ -weightings and  $k$ -ranges between 2 and 12  $\text{\AA}^{-1}$  and between 2 and 9  $\text{\AA}^{-1}$  were used for the 300 K data and 723 K data, respectively, in Fourier transforms.

elsewhere, the oxidation of perthiometalates characteristically leads to reduction of the metal concomitant with coupling of the sulfido ligands. For example, the oxidation of  $\text{MoS}_4^{2-}$  gives  $[\text{Mo}_2(\text{S}_2)_6]^{2-}$  and  $[\text{Mo}_2\text{S}_4(\text{S}_2)_2]^{2-}$ .<sup>48</sup>

**Structural Proposals for  $\text{Re}_2\text{S}_7$  and  $\text{ReS}_4$ .** The fact that of our XAS analyses accurately reproduce the structural characteristics of the reference compounds  $\text{ReS}_2$  and  $\text{Et}_4\text{NReS}_4$  provided a critical test prior to the XAS analysis of the amorphous materials  $\text{Re}_2\text{S}_7$  and  $\text{ReS}_4$ . The close similarity of  $\text{Re}_2\text{S}_7$  and  $\text{ReS}_4$  is strongly indicated by the XAS data, as well as their TGA behavior. Beyond these facts, the structural assignments for the local structures of the  $\text{Re}_2\text{S}_7$  and  $\text{ReS}_4$  phases were guided by the following considerations: (i) XAS data show the presence of both  $\text{S}^{2-}$  and  $\text{S}_2^{2-}$ , with  $\text{S}^{2-}$  being less abundant than  $\text{S}_2^{2-}$ . Sulfur is not present as  $\text{S}^0$  (see  $\text{S}_3^{2-}$  as found in  $(\text{C}_5\text{Me}_5)\text{Re}(\text{S}_3)\text{Cl}_2$ ).<sup>49</sup>(ii) Rhenium sulfides of nuclearity  $> 2$  characteristically contain triply bridging  $\mu_3\text{-S}$ .<sup>18</sup> (iii) Whereas EXAFS cannot distinguish  $\mu_2\text{-S}$  vs  $\mu_3\text{-S}$ , the absence of short Re–S contacts combined with the unimodal distribution


of Re–S bond lengths rules out terminal sulfides ( $r_{\text{Re}=\text{S}} \sim 2.14 \text{ \AA}$ ). (iv) The Re oxidation state is expected to lie between  $4^+$  (as in  $\text{ReS}_2$ ) and  $5^+$ . The anion  $\text{ReS}_4^-$  is the unique example of a  $\text{Re}^{\text{VII}}$  sulfide, but it is stabilized by four terminal sulfido ligands, which are powerful  $\pi$ -donor ligands. At the other extreme, the octahedral Chevrel-like rhenium sulfide clusters exist in the  $3^+$  oxidation state,<sup>18</sup> but this structure type is inconsistent with the EXAFS data.

The above considerations lead to two idealized compositions (based on integral Re oxidation states) for  $\text{Re}_2\text{S}_7$ :  $\text{Re}^{\text{IV}}(\text{S})_{0.5}(\text{S}_2)_{1.5}$  and  $\text{Re}^{\text{V}}(\text{S})_{1.5}(\text{S}_2)_1$ . Correspondingly, two idealized formulas are indicated for  $\text{ReS}_4$ ,  $\text{Re}^{\text{V}}(\text{S})_1(\text{S}_2)_{1.5}$ , and  $\text{Re}^{\text{VI}}(\text{S})_2(\text{S}_2)_1$ . EXAFS measurements indicate that  $\text{Re}_2\text{S}_7$  and  $\text{ReS}_4$  may differ in the degree of Re–Re bonding (CN of  $\sim 2$  and  $\sim 3$ , respectively), although it is difficult to rationalize more than two localized Re–Re bonds per  $d^2$  metal center. The proposed structures are proposed to be members of a stoichiometric continuum  $\text{Re}^{\text{V}}(\text{S})_{1.5-1}(\text{S}_2)_{1-1.5}$  that differ in the  $\text{S}^{2-}/\text{S}_2^{2-}$  ratio (Figure 7).

The structures proposed for  $\text{Re}_2\text{S}_7$  and the new phase  $\text{ReS}_4$  are interesting from a number of perspectives. Low-dimensional structures of this sort are consistent


(48) Stiefel, E. I. *Pure Appl. Chem.* **1998**, *70*, 889–896.

(49) Herberhold, M.; Jin, G. X.; Milius, W. *Z. Anorg. Allg. Chem.* **1994**, *620*, 299–303.

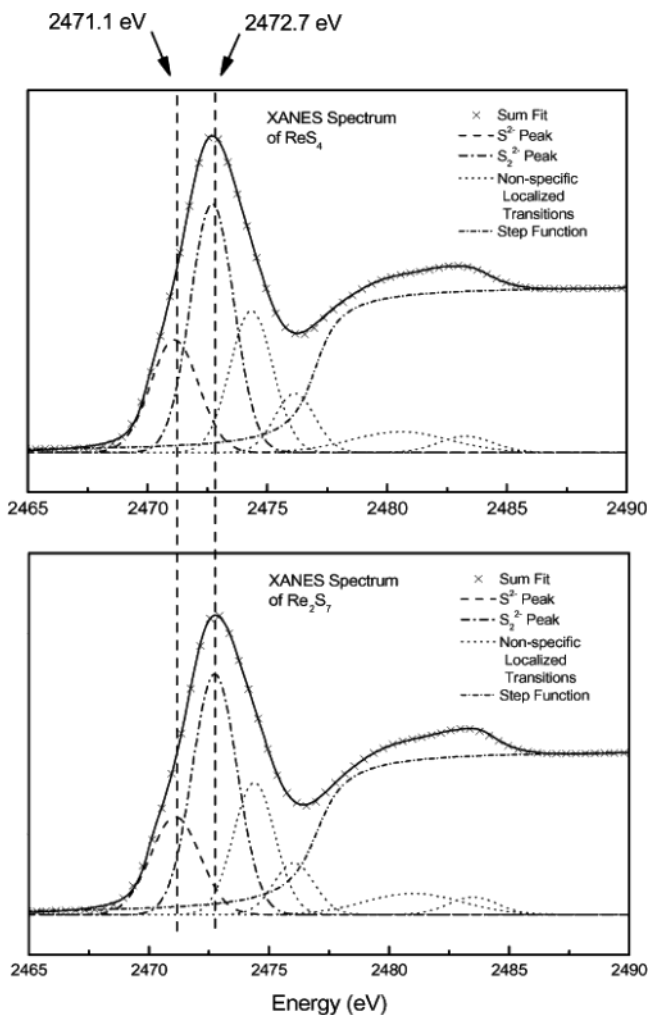

**Figure 6.** Fits for the S K-edge data showing the presence of sulfur as  $S^{2-}$  (2471.1 eV) and  $S^-$  in  $ReS_4$  (2472.7 eV).

with the finding that  $ReS_4$  can be reversibly reduced (albeit with significant overpotential) to  $ReS_4^-$ . A low-dimensional structure may also be relevant to the high catalytic activity of  $Re_2S_7$ , due to the intrinsically higher surface area. One attraction to such sulfur-rich phases

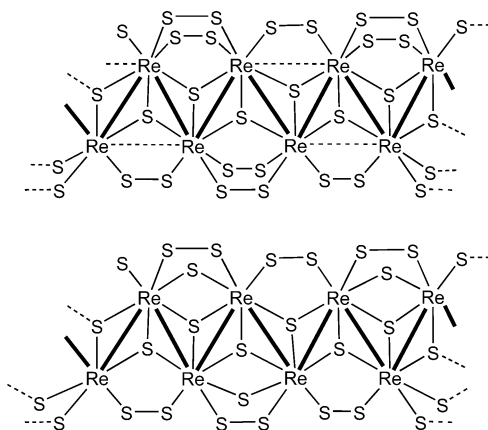

**Figure 7.** Structural proposal for  $Re_2S_7$  (top) and  $ReS_4$  (bottom), with the compositions  $Re^V(S)_{1.5}(S_2)_1$  and  $Re^V(S)(S_2)_{1.5}$ , respectively.

is that they should be amenable to surface functionalization exploiting the reactivity inherent in the persulfido ( $S_2^{2-}$ ) functionality.<sup>50,51</sup> These considerations encourage us to further explore electrochemical routes to other sulfided phases from other sulfur-rich monomers and their surface functionalization.

**Acknowledgment.** This research was funded by NSF (T.B.R.) and through the Frederick Seitz Materials Research Laboratory at the University of Illinois (DEFG02-91ER45439). A.I.F. and R.G.N. acknowledge support by the U.S. Department of Energy Grant DE-FG02-03ER15477. We thank Dr. J. T. Goodman for preliminary results on the electro-oxidation of  $ReS_4^-$ . A.V. acknowledges support by the Division of Geosciences of the Basic Energy Sciences, and the NABIR Program, Office of Biological and Environmental Research, U.S. Department of Energy, under Contract DE-AC02-98CH10886 to Brookhaven National Laboratory.

CM034467V

(50) Bolinger, C. M.; Weatherill, T. D.; Rauchfuss, T. B.; Rheingold, A. L.; Day, C. S.; Wilson, S. R. *Inorg. Chem.* **1986**, *25*, 634.

(51) Seyferth, D.; Henderson, R. S.; Song, L. C. *Organometallics* **1982**, *1*, 125–133.